




## RheoGel 2105

RheoGel 2105 is carefully balanced low noise grease to provide friction reduction, wear prevention, extreme pressure performance, low temperature performance, and ferrous corrosion protection. This grease has been designed for wide temperature automotive and industrial applications and is recommended from -50°C to 150°C.

BASE OIL CHARACTERISTICS		TYPICAL VALUE *
<b>Type</b>		Synthetic Hydrocarbon
<b>Temperature Service Range (°C)</b>		-50 to 150
GREASE CHARACTERISTICS		TYPICAL VALUE *
<b>Thickener</b>		Lithium
<b>Color</b>		White
<b>Appearance</b>		Smooth
<b>NLGI Grade</b>		2
<b>Penetration (ASTM D217 / DIN 51804-T1)</b>	Unworked	265-295
	Worked	60X 265-295
<b>Dropping Point (°C) (ASTM D2265 / DIN ISO 2176)</b>		200 min.
<b>Oil Separation (ASTM D6184)</b>	24h at 100°C	5% max.
<b>Evaporation (CTM-1)</b>	24 at 100°C	1% max.
<b>Water Washout (ASTM D1264 / DIN 51807-T2)</b>	60 min at 41°C	0.80%
	60 min at 79°C	4.00%
<b>Bearing Corrosion (ASTM D1743)</b>	48h at 52°C, 5% NaCl solution	Pass
<b>Copper Corrosion (ASTM D130 / DIN 51811)</b>	24h at 100°C	1a
<b>Corrosion Protection (EMCOR)</b> SKF EMCOR method ISO 11007 DIN 51 802 IP 220	168h w/alternating running & stop periods 80 rpm; 5% NaCl solution; 11 cm <sup>3</sup> per bearing	#0
<b>Four Ball Wear (ASTM D2266 / DIN 51350-T5)</b>	60 min 1200 RPM 75°C 40kg <sub>r</sub>	0.45mm
<b>Four Ball EP (ASTM D2596)</b>	LNSL	63 kg
	LSL	126 kg
	WP	160 kg
	LWI	27.77
<b>Fretting Wear (ASTM D4170)</b>	Axial load: 8000N (Hertzian pressure 2100 N/mm <sup>2</sup> ) Duration of test: 5 or 50 h Frequency: 24 Hz Oscillation angle: ±3° Temperature of lower bearing ring: -20°C or +25°C	3.2 mg
<b>Oxidation Stability (ASTM D942 / DIN 51808)</b>	100h at 100°C	3 psi

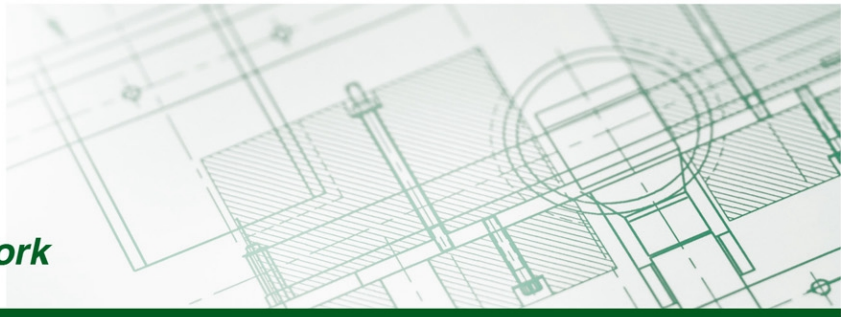

## RheoGel 2105

<b>Low Temperature Torque</b> (ASTM D1478)	-40°C	Start	858 g.cm
		Run 60 min	208 g.cm
<b>Low Temperature Apparent Viscosity</b> (ASTM D2196 or CTM-3 (Brookfield))	-40°C, T-C spindle, 1rpm (7,000,000 max)		2,410,000 cP
<b>Flow Pressure of Lubricating Grease</b> (DIN 51 805)	-40°C		5.01 psi 10.38 inches Hg 141.2 inches H <sub>2</sub> O 35.16 kPa 351.6 mbar
<b>FE 8 Rolling Bearing Fatigue Test</b> (DIN 51 819)	Test bearing: two Angular Contact Ball Bearings size 7206 (FE9 bearing) • Load: 30 kN • Speed: 750 rpm • Temperature: 80°C • Capacity of grease: 6 ml each bearings		517 Hours
<b>SKF Be Quiet Grease Noise Test, (µm/s)</b>	Duration of test: approx. 40 min, standard test Pickup: speed sensor Speed: 1800rpm Axial load: 30N (pneumatic) Test with: 1 bearing (standard) Grease quantity: automatic time-related metering, approx. 150 mg L: 50-300 Hz M: 300-1800 Hz H: 1800-10000 Hz Peak filter: pre 300 to 10000 Hz Post 25 to 400 Hz Display: µm/s: peak Acoustic monitoring via loudspeaker		GN1

### Engineered Custom Lubricants

ISO/TS16949:2009 • Registered QMS

3851 Exchange Ave. • Aurora, IL 60504 • T: 630.449.5000 • F: 630.585.0050 • E: [customerservice@ecllube.com](mailto:customerservice@ecllube.com) • [www.ecllube.com](http://www.ecllube.com)

DISCLAIMER: Since we cannot anticipate or control the many different conditions under which this information and our product may be used, we cannot guarantee the applicability of this information or the suitability of our product in any individual situation. For the same reason, the product discussed is sold without warranty expressed or implied. Please contact Engineered Custom Lubricants for assistance and recommendations prior to writing or releasing any engineering specifications. ECLI Products, LLC, owns and does business as Engineered Custom Lubricants and Lubrication Technology.